



***Society of Cable
Telecommunications
Engineers***

**ENGINEERING COMMITTEE
Interface Practices Subcommittee**

AMERICAN NATIONAL STANDARD

ANSI/SCTE 13 2011

**Dielectric Air Leakage Test Method
For Trunk, Feeder and Distribution Coaxial Cable**

NOTICE

The Society of Cable Telecommunications Engineers (SCTE) Standards are intended to serve the public interest by providing specifications, test methods and procedures that promote uniformity of product, interchangeability and ultimately the long term reliability of broadband communications facilities. These documents shall not in any way preclude any member or nonmember of SCTE from manufacturing or selling products not conforming to such documents, nor shall the existence of such standards preclude their voluntary use by those other than SCTE members, whether used domestically or internationally.

SCTE assumes no obligations or liability whatsoever to any party who may adopt the Standards. Such adopting party assumes all risks associated with adoption of these Standards or Recommended Practices, and accepts full responsibility for any damage and/or claims arising from the adoption of such Standards or Recommended Practices.

Attention is called to the possibility that implementation of this standard may require use of subject matter covered by patent rights. By publication of this standard, no position is taken with respect to the existence or validity of any patent rights in connection therewith. SCTE shall not be responsible for identifying patents for which a license may be required or for conducting inquiries into the legal validity or scope of those patents that are brought to its attention.

Patent holders who believe that they hold patents which are essential to the implementation of this standard have been requested to provide information about those patents and any related licensing terms and conditions. Any such declarations made before or after publication of this document are available on the SCTE web site at <http://www.scte.org>.

All Rights Reserved

© Society of Cable Telecommunications Engineers, Inc. 2011
140 Philips Road
Exton, PA 19341

1.0 SCOPE

- 1.1. The purpose of this test is to detect voids in the dielectric and the bond between the dielectric and the center conductor.

2.0 NOTES AND PRECAUTION

- 2.1. Check the calibration label on each piece of test equipment to insure that the test equipment used is within calibration period limits.

3.0 EQUIPMENT

- 3.1. Safety Glasses
- 3.2. Cable Cutters
- 3.3. Tubing Cutters
- 3.4. Band Saw
- 3.5. Water Container and Distilled Water
- 3.6. Air Transmission Regulator (Capable of Maintaining 5 PSI)
- 3.7. Adapter Capable of Connecting Cable to Airline (Including: Air Valve Stem, Rubber Boot, Hose Clamp). Reference Figure 1 or Equivalent.

4.0 DIAGRAM

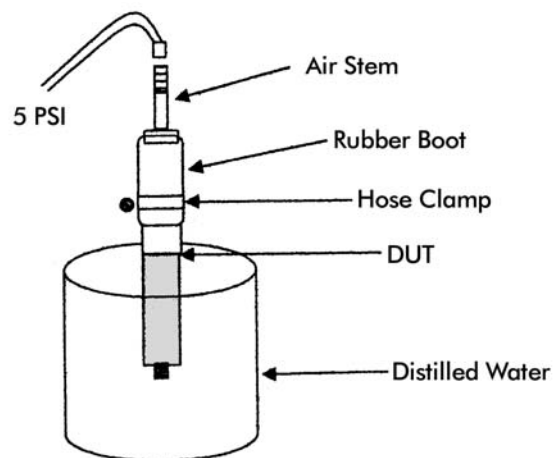


Figure 1

5.0 TEST METHOD

- 5.1. Cut a $14'' \pm 0.25''$ ($35.6 \text{ cm} \pm 6.4 \text{ mm}$) specimen of product to be tested with cable cutters. Remove the jacket where applicable. Using a knife or tubing cutters, score the outer aluminum shield five inches from one end of the specimen. Peel away the outer sheath using diagonal cutters. Remove $0.5'' \pm 0.125''$ ($1.27 \text{ cm} \pm 3.2 \text{ mm}$) of the outer aluminum shield and dielectric material on the opposite end, exposing the center conductor. With a band saw, square the dielectric end to reveal a specimen length of $12'' \pm 0.25''$ ($30.5 \text{ cm} \pm 6.4 \text{ mm}$).
- 5.2. Insert the exposed dielectric into the corresponding adapter. Do not over tighten the hose clamp. Assure that no leaks are present between the adapter and the specimen or any other connection.
- 5.3. Submerge approximately $2'' \pm 0.25''$ ($5 \text{ cm} \pm 6.4 \text{ mm}$) of the exposed cable end into the water container. Note: Remove all trapped air from the submerged specimen.
- 5.4. Using $5 \text{ PSI} \pm 0.25 \text{ PSI}$ ($34.5 \text{ kpa} \pm 1.7 \text{ kpa}$), submit the specimen to air for 15 seconds.

6.0 INSPECTION

No bubble is to release from the end of the specimen and rise to the water surface during the 15-second test.

7.0 REPORTING

Note if any air bubbles were present.